

Mixed matrix membranes of 6FDA-6FpDA with surface functionalized γ -alumina particles. An analysis of the improvement of permselectivity for several gas pairs

A. Tena^{b,d}, L. Fernández^a, M. Sánchez^a, L. Palacio^{b,d}, A.E. Lozano^{c,d}, A. Hernández^{b,d}, P. Prádanos^{b,d,*}

^a Dpto. de Química, Facultad de Ingeniería, Universidad Nacional del Comahue, Buenos Aires 1400–8300, Neuquén, Argentina

^b Dpto. Física Aplicada, Facultad de Ciencias, Universidad de Valladolid, Real de Burgos s/n, 47071 Valladolid, España

^c Instituto de Ciencia y Tecnología de Polímeros, CSIC, Juan de la Cierva 3, 28006 Madrid, España

^d Surface and Porous Materials (SMAP), UA-CSIC-UVA, R&D Building, Belén s/n, Campus Miguel Delibes, 47071 Valladolid, España

ARTICLE INFO

Article history:

Received 13 August 2009

Received in revised form

16 December 2009

Accepted 18 December 2009

Available online 4 January 2010

Keywords:

Gases

Separations

Membranes

Nanostructure

Permselectivity

Diffusion

ABSTRACT

Herein, mixed matrix membranes including alumina particles whose surfaces have been differently modified have been made and characterized. The polymeric matrix is a fluorinated polyimide, 6FDA-6FpDA, whereas the inorganic constituent parts are neat, silanized or poly-vinyl-pirrolidone-coated nanometric γ -Al₂O₃ particles of 40 nm in diameter, which have been added in an approximated percentage of a 12% w/w.

All the modified or unmodified added particles lead to similar improvements in the permselectivity of the gas pairs studied. Only in the case of the O₂/N₂ pair the increase in selectivity for the silanized particles is not as effective as the observed permeability enhancement for the uncoated and PVP-coated particles. In case of CO₂/CH₄, the 1991 Robeson's upper bond line is overpassed.

The characteristics of the permselectivity improvement for the different inorganic particles have been analyzed in terms of the properties of the particle–polymer interfacial properties.

© 2009 Elsevier Ltd. All rights reserved.

1. Introduction

Two of the main contaminants of the natural gas are the CO₂ and N₂, which used to be naturally present in the rocks. In addition, CO₂/CH₄ and N₂/CH₄ separation could be needed as a consequence of using high pressure gases during extraction procedures. Thus, pressurized N₂ is used to increase the recovery of hydrocarbons in some oilfields. In this way, and according to the high cost of oil nowadays the commented separations play a relevant role not only for this secondary oil extraction procedure but also have a relevant role in tertiary oil extraction when the oil viscosity is reduced to increase its production by injecting hot gases into the reservoir or when the carbon dioxide flooding method is used Chilingar et al., 1989. This method consists of injecting pressurized CO₂ when the natural gas reservoir pressure is depleted through primary and secondary production to take advantage of their very good solvent properties. CO₂ flooding is the second most common tertiary recovery technique and it is used in facilities around the world. CO₂/CH₄ gas separation also

plays a very important role in the transport of natural gas through pipelines where sour gases could be very problematic.

The conventional gas treatment plants have byproducts consisting of both liquid and gas fraction. The gas streams contain high proportions of natural gas with some percentages of other non-condensable gases as CO₂, N₂ or others depending on the specific treatment and raw product used. These gases should be eliminated in order to increase the calorific power of such a gas stream. Other applications of the CO₂/CH₄ and N₂/CH₄ gas separations can be found in many processes in refinery, petrochemical processing, etc... Speight, 1999; Li et al., 2008.

In the scope of global warming, CO₂ flooding seems an available method to curb CO₂ emissions, Chilingar et al., 1989. An extensive use of such a procedure to eliminate CO₂ from the emissions of power plants should need several gas separation steps including the CO₂/N₂ one.

Membranes can be used to recover methane from biogases such as landfill, which composition of N₂ and CO₂ can be high. These separations can also play a relevant role to control the composition of several pyrolytic and cogeneration gaseous streams, Van Loo and Koppejan, 2008. In direct conversion of biomass to hydrocarbons, N₂ and CO₂ need to be separated from light hydrocarbons.

On the other hand, there is a big market for the O₂/N₂ separation to obtain NEA (nitrogen enriched air) and/or (oxygen

* Corresponding author. Dpto. Física Aplicada, Facultad de Ciencias, Universidad de Valladolid, Real de Burgos s/n, 47071 Valladolid, España. Tel.: +34 983423739; fax: +34 983423136.

E-mail address: pradanos@termo.uva.es (P. Prádanos).

enriched air) OEA, mainly to improve the coal burning in thermal power plants, Puri, 1996. These applications include the obvious medical ones but also some applications in the industry where the oxidizing or inert character of a gaseous stream has to be tuned, Li et al., 2008; Stookey, 2006. An example of such kind of applications is the control of the process of pyrolysis of biomass, Van Loo and Koppejan, 2008.

At present, membranes for gas separations are an interesting alternative by using polymeric materials. Nevertheless, there are a number of possible itineraries addressed to improve the permeability and selectivity of gas separation membranes. One of them tries to optimize the structure of the polymer chains to give high volume fractions with restrictive or selective channels communicating the voids in order to increase the diffusivity. Other possible approach consists of attempting to increase the solubility introducing a certain chemical affinity for a gas to make it to adsorb on certain moieties of the polymer. An alternative and promising line involves the addition of inorganic micro or nanoparticles in a polymeric matrix whose permselective properties were already good in order to improve them yet more, Marchese et al., 2006; Cecopieri-Gómez et al., 2007. These resulting membranes are called mixed matrix membranes.

Apart from the contribution of both the bulk phases, inorganic and polymeric materials, the interfaces between such phases play a relevant role. Herein, we are obtaining mixed matrix membranes that include several inorganic particles differently coated in order to modify the resulting polymer–particle interfaces. Our aim has been to compare these systems to separate N_2/CH_4 , CO_2/CH_4 , CO_2/N_2 and O_2/N_2 and also to figure out, how they improve the characteristics of the neat polymeric matrix.

The incorporation of filling materials can increase or decrease the transport of one or several gases through the mixed matrix membrane when compared to that of the polymeric matrix alone. Obviously, the shape, the size and the chemical nature of the filling particles plays a key role on the transport properties.

The transport, i.e. the permeability and or the selectivity can get better because:

- The particles inserted within the polymeric matrix present better permeability or selectivity than the polymeric matrix in such a way that the addition of their properties lead to better overall transport properties, Marchese et al., 2006; Anson et al., 2004; Vu et al., 2003a, b.
- The characteristics of the interface between the filling material and the polymer could increase or decrease the path to be traveled by one of the gases over the rest of them. This should increase the selectivity, or it could decrease the length to be covered by all the gases, which should increase the permeability, Zimmerman and Koros, 1997.
- The particles could modify the properties of the neighbor polymer phase, which should favor its permeability or its selectivity (Tartekin-Ersolmaz et al., 2000; Jia et al., 1991). In some cases, for particles very well distributed or spread within the polymeric matrix, the modifications of fractional free volume could affect the polymeric phase (Merkel et al., 2002, 2003; Chung et al., 2003).

When particles with very good permselective properties, as for example zeolites, are used as fillers, better selectivities are obtained while permeability does not necessarily increase Sen et al., 2007. When there is a better compatibility of the particles with the polymeric matrix, as for example when active carbon is used, there exists a simultaneous improvement of selectivity and permeability Marchese et al., 2006. For non-permeable particles an increase in permeability leads to a decrease in selectivity,

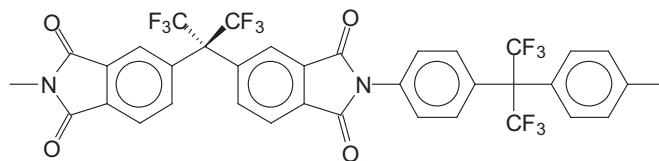


Fig. 1. Chemical structure of the 6FDA-6FpDA.

especially when there is also a lack of adhesion of filler and matrix Matteucci et al., 2008a. This effect is more remarkable when a pair of lowly condensable gases is used. If both the gases are highly condensable, as for example n-butane/methane both permeability and selectivity increase by using silica particles in a PMP matrix He et al., 2002.

Here the 6FDA-6FpDA polymer, Fig. 1, has been modified by the incorporation of γ -alumina particles with a nominal diameter in the range from 45 to 50 nm. The particles were included without any modification or with different moieties covalently bonded to their surfaces. The grafted materials were a silane network and a poly-vinyl-pyrrolidone attached to the surface through a silane link, Fernández et al., 2009. In our case the neat particles are dense and cannot be penetrated by any of the gases studied. Thus their effect could consist only in: (a) modification in the permeability or selectivity of regions of the polymeric matrix due to a distortion of its structure induced by the particles, (b) increase or decrease in the path to be followed by the gas through the membrane due to the specific solubility (the coating could introduce some chemical affinity) or (c) changes in diffusivity (modifications in the free volume) at the interface between the polymer and the particle surface. We will see how, in our case, the permeability increases without a simultaneous decrease and sometimes with a moderated increment of selectivity. How those mechanisms act for the different gases and particles used will be analyzed below.

2. Experimental

2.1. Polymer matrix

The polymer chosen to constitute the polymeric matrix of our mixed matrix membranes is the 6FDA-6FpDA, made from 4,4'-(hexafluoroisopropylidene)diphthalic Anhydride (6FDA) and 4,4'-(hexafluoroisopropylidene)dianiline (6FpDA), of which the chemical structure is shown in Fig. 1. 6FDA-6FpDA is a fluorinated polyimide presenting by itself good gas separation properties, Van Krevelen and te Nijenhuis, 2009; Recio et al., 2006; Recio et al., 2007, good mechanical, thermal and transport properties, Coleman and Koros, 1999. It also shows an appreciable resistance to plasticization, Nagel et al., 2002.

This polyimide was synthesised by us following the classical in situ silylation two steps method from the 6FpDA diamine and the 6FDA dianhydride, Khulbe et al., 1997; Wang et al., 2005; Muñoz et al., 2007. The intrinsic viscosity of the so obtained polymer is 0.62 dL/g.

2.2. Inorganic nanoparticles

The used γ -alumina particles were: (a) untreated, (b) silanized and (c) coated with poly-vinyl-pyrrolidone (PVP) attached through a silane linker. The particles of γ -alumina ($(\gamma-Al_2O_3)$) are non-porous ones with average diameters from 45 to 50 nm according to the specifications given by the manufacturer (Sigma, CAS 1344-28-1).

The particles have been silanized by the method described by Yoshida et al., 2001. In a 500 mL reactor, a 80 g/L water solution of the particles was added on a 10% (v/v) solution of vinyltrimethoxysilane (VTMS) (Fluka, 95095) in a mixture of isomers of xylene (Fluka, 9560). The mixture was kept at 130 °C and stirred during 5 h. The vapors produced are condensed at 75 °C and the produced methanol was stripped off. A scheme of the reaction is shown in Fig. 2A.

Once the nanoparticles were silanized, they were coated with PVP by two consecutive steps. The process consists in a hydrolysis of the methoxy groups followed by a polymerization of the vinyl group. The hydrolysis is achieved by keeping the silanized γ -alumina particles during 3 days in a stirred NaOH aqueous solution at pH 9.5 and ambient temperature. In Fig. 2B the so-produced reaction of hydrolysis is shown. Afterwards, 1-vinyl-2-pyrrolidone (Fluka, 95060) was free-radical-polymerized in an aqueous medium with the silanized and hydrolyzed particles. The reaction was started by a 30% water solution of oxygen peroxide with a water solution of ammonia (24° Be) as a co-catalyst in a reactor under a nitrogen atmosphere to reduce the latency period and to increase the rate of polymerization. About 5 g of hydrolyzed particles were poured and dispersed in 200 mL of the co-catalysts solution and kept at 70 °C (due to the exothermic behavior of the reaction, its refrigeration is required). Finally, the reaction was stopped by adding Milli-Q treated water. The reaction is shown in Fig. 2C.

The productivity of the reactions was evaluated by Thermogravimetry (TGA) leading to 0.48 mg/m² for the silylation and to 2.31 mg/m² for the polymerization, Fernández et al., 2009. The silanized particles were washed with xylene solvent and then

recovered by rota-evaporation. The PVP covered particles were separated from the unlinked PVP by centrifugation.

The size of the particles has been determined from the specific surface area (BET area) and the density of all the materials constituting the core and the deposited layers by assuming pure spherical geometry. The BET area was evaluated by using the Brunauer–Emmett–Teller theory and the nitrogen adsorption isotherms at 77 °C determined in an Omnisorp 100 CX by Coulter®. The values for the surface area (S_s) and the diameter of the particle (d_p) are shown in Table 1. It is clearly seen that the surface area decreases when more and more PVP layers are added. On the other hand, the size of the alumina particles is very similar to that given by the manufacturer, with a slight increment for the silanized ones and a more substantial growth in diameter after the PVP coating, Fernández et al., 2009. Fig. 3 shows the three types of particles obtained after the treatment.

2.3. Membrane manufacture

The membranes were manufactured by using tetrahydrofuran (THF) as solvent, stabilized with 250 ppm of 2,6-Di-tert-butyl-4-methylphenol (BHT). A 15% w/v solution of the polymer in THF was mixed with the same volume of a 2% w/v suspension of the particles in THF. The solution of polymer was prepared by vigorous stirring and filtered with a 1 μ m (Titan, PTFE) membrane. The suspension was made by treating the combined solution and suspension with ultrasounds by means of a sonic horn.

The films were obtained by the method of casting on a levelled glass plate kept at 25 °C. Afterwards they were kept at 60 °C

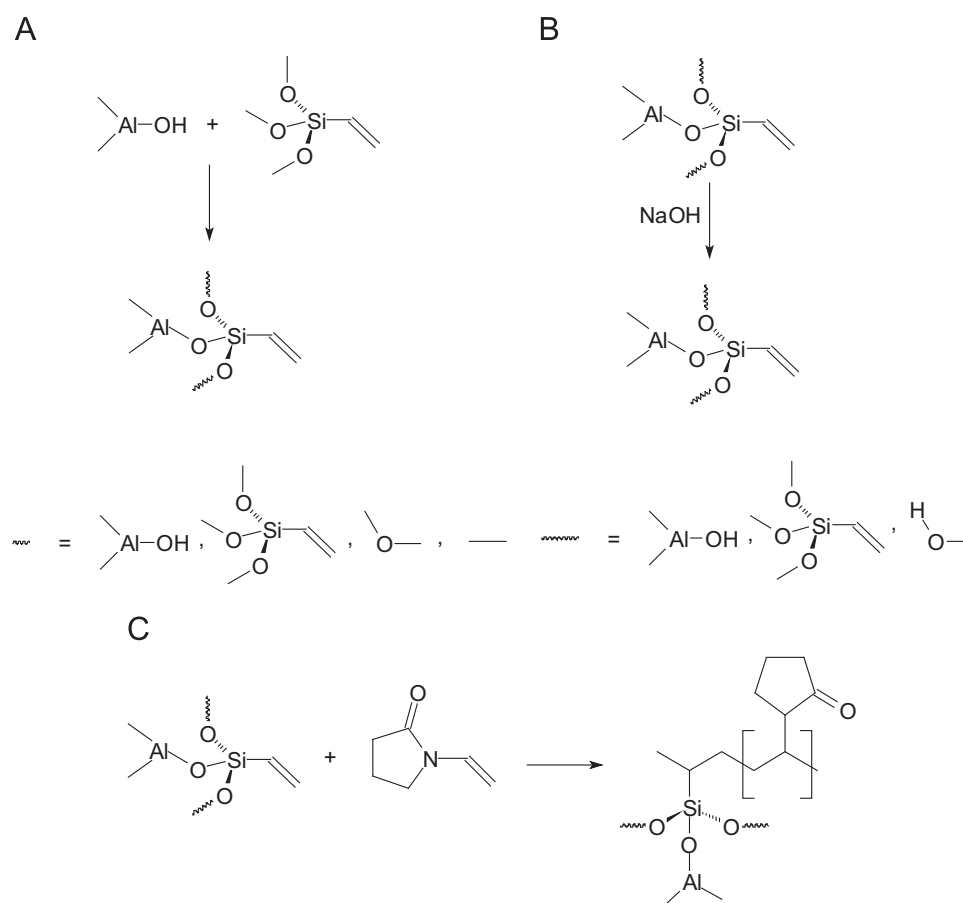


Fig. 2. Silylation reaction (A), hydrolysis of methoxy groups (B) and polymerization reaction (C).

during 12 h and later at 80 °C for 1 h in order to completely eliminate the solvent. The so-obtained films were separated from the glass by immersion in distilled water and introduced in a vacuum oven at 180 °C where they were maintained for 24 h. The used proportion of particles obtained is shown in Table 2. After these treatments the membranes were ready to measure their permeabilities for different gases and to evaluate the corresponding permselective properties. Images, obtained by SEM, of cross-sections of the membranes with and without the filling particles, are shown in Fig. 4. It is easily seen that there is a worst adherence of the polymer and the particles when they are uncovered.

2.4. Measurements of permeability

The permeability, P , for the N_2 , CO_2 and CH_4 gases has been determined by using a permeator with constant volume and variable pressure which uses the “time-lag” operation method. The measurements have been carried out at 3 bar and 30 °C, Marchese et al., 2006. In Fig. 5 a drawing of the used device is shown.

Table 1
Specific surface areas and particle diameters.

Treatment	S_s (m ² /g)	d_p (nm)
Unmodified particles of alumina	37.75	39.72
Silanized alumina	29.29	51.20
PVP coated particles	25.70	177.4

The strategy known as “time-lag” method is attributed to Daynes, 1920, and it is able to determine permeability, diffusivity and solubility of a sample by a simple, rapid and smart method working under transitory regime. The method was successfully applied to polymer permeation by Paul and DiBenedetto, 1965, Crank, 1975, and Barrer and Skirrow, 1984. It is nowadays a classical method to assess the permeability and diffusion coefficients of a gas through a polymer film for a given set of operating conditions (temperature and pressure). To sum up, the classical treatment postulates, among others, Fick’s law to hold with a constant diffusion coefficient and constant membrane thickness (i.e. negligible swelling effect exerted by the permeant). When these conditions are prevailing, the transitory response at the downstream part of a membrane to a pressure step at the upstream part enables a characteristic time to be easily computed from experimental data, the time-lag, t_0 , (shown in Fig. 6). This parameter gives access to the permeant diffusion coefficient, D , through the simple expression, Crank, 1975

$$t_0 = \frac{\Delta x^2}{6D} \quad (1)$$

Δx being the thickness of the membrane.

The amount of gas transmitted at time t through the membrane was calculated from the permeate pressure, p_2 , readings in the low-pressure side. The inherent leak rate in the downstream side determined after evacuating the system was measured for each experimental run. The permeability constant can be obtained directly from the flow rate into the downstream volume upon reaching the steady state. The theoretical

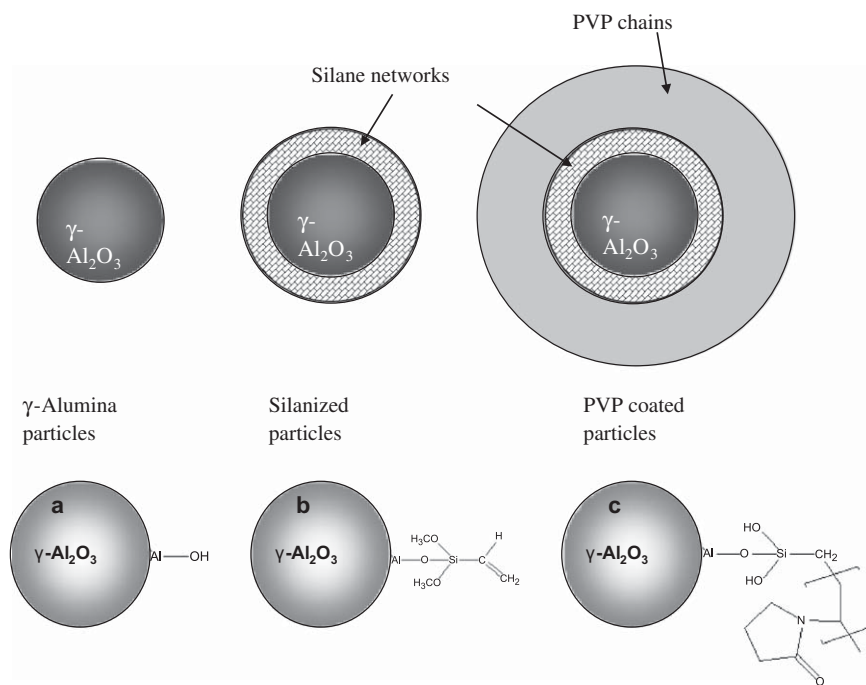


Fig. 3. Sketch of the particles used and their coating layer showing the chemical structure on their surfaces.

Table 2
Manufactured membranes with similar w/w percentages of differently treated particles.

Membrane	6F6FpDA weight (g)	Weight of particles (g)	% (w/w)
Unmodified particles of alumina	0.5998	0.0805	11.83
Silanized alumina	0.6022	0.0800	11.72
PVP coated particles	0.6090	0.0795	11.54

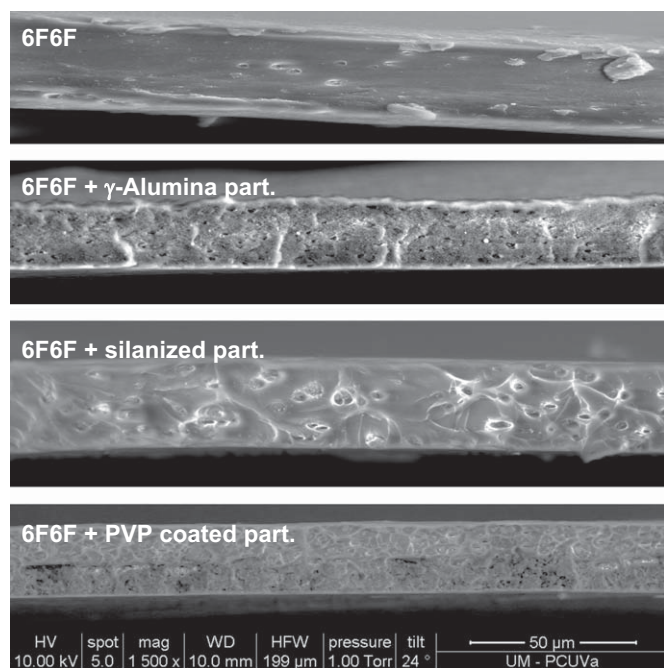


Fig. 4. SEM images of cross-sections of the membranes studied.

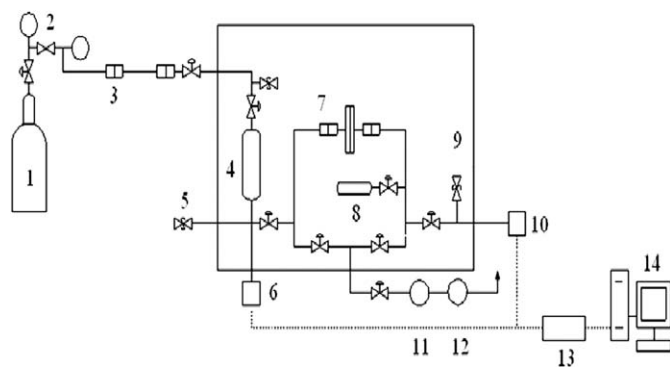


Fig. 5. Diagram of the permeation device: (1) Gas supply, (2) Pressure regulator, (3) Quick connection, (4) Gas reservoir, (5) Relief valve, (6) High pressure transducer, (7) Permeation cell, (8) Expansion cylinder, (9) Relief valve, (10) Low pressure transducer, (11) Turbo-molecular pump, (12) Rotary pump, (13) Power source and (14) Data acquisition.

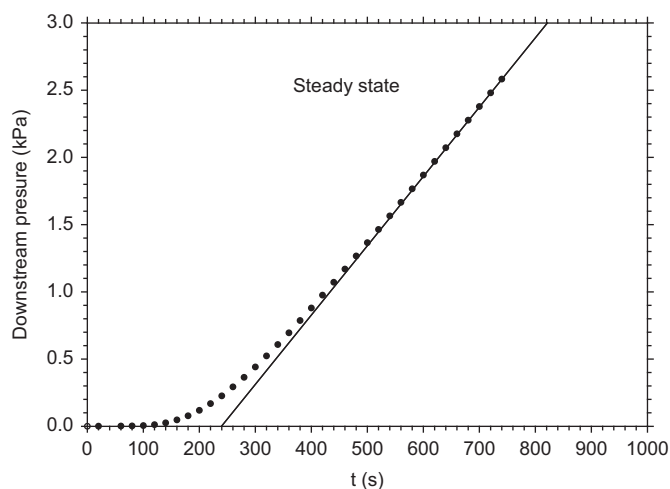


Fig. 6. An example of the time lag plots obtained.

framework, as well as the practical possibilities and limits of the time-lag technique have been abundantly documented, Rutherford and Do, 1997; Yeom and Kim, 1999; Favre et al., 2002.

Finally, solubility, S , can be obtained from directly measured diffusivities and permeabilities as

$$S = \frac{P}{D} \quad (2)$$

3. Results and discussion

In Fig. 7A–D the corresponding Robeson representations of selectivity versus permeability are shown for the gas pairs studied here. Note that, for the CO_2/CH_4 and N_2/CH_4 , the inclusion of the silanized particles lead to an increase in selectivity with only a moderate increase in permeability of the most permeable gas in the pair while the unmodified γ -alumina as well as the PVP coated particles lead to high increments in permeability but with a very low effect on selectivity. For the pairs not including methane, i.e. for O_2/N_2 and CO_2/N_2 , the permeability for the most permeable gas in the pair is also moderated for the mixed matrix membranes including silanized particles but the selectivity is almost constant. For these pairs of gases, the other mixed matrix membranes, including uncoated γ -alumina or the PVP coated particles, give bigger permeabilities for the most permeable component of the analyzed pair, with the same low effect on selectivity.

In all these figures, the corresponding Robeson's bond lines are shown both as predicted in 1991, Robeson, 1991, and in 2008, Robeson, 2008. Note that for the pairs N_2/CH_4 and CO_2/N_2 no limits were proposed in the original 1991 work of Robeson. In any case, it is clear that very good results are obtained for the CO_2/CH_4 pair. Moreover, it is worth noting that very similar performances are obtained for all the mixed matrix membranes studied, since all of them surpass the old Robeson's bond. For the other pairs of gases, the results are good enough in all cases but especially for the membranes including PVP coated or unmodified γ -alumina particles mainly due to the high permeabilities reached in these cases. In all these cases (naked and PVP coated particles), increments in permeability around 50% are obtained for CO_2 , N_2 , and O_2 and of a 30% for CH_4 , with moderate increments in selectivity. Lower increments in permeability are found in literature when non-porous fillers are used as for example TiO_2 , MgO or ZnO as used by Matteucci et al. with similar percentages to those used here, Matteucci et al., 2008a; Matteucci et al., 2008b; Matteucci et al., 2008c.

The changes in both the selectivity and the most permeable gas permeability, when including inorganic porous charges (as zeolites for example) into a polymeric matrix have been analyzed by Moore and Koros, 2005. They attribute comparatively large increases in permeability with no or low changes in selectivity owing to a poor adhesion of the polymer to the surface of the particles leaving voids or a high free volume phase forming a *halo* around the particles acting as an interface that do not add any selectivity. When the size of the voids in the *halo* are of the order of the mean free paths of the permeant gases, the permeation across the material of the *halo* follows a Knudsen regime that favours the lighter gas and thus should slightly decrease the selectivity. When the size of the voids is similar to the size of the gas molecules both the diffusion and solubility across the voids should be very low and the corresponding solubility should pass through a minimum. On the other hand, when neither the pores in the sieve particles nor the free volume of the polymer are modified, the Maxwell model should predict a simultaneous increase of selectivity and permeability given that the

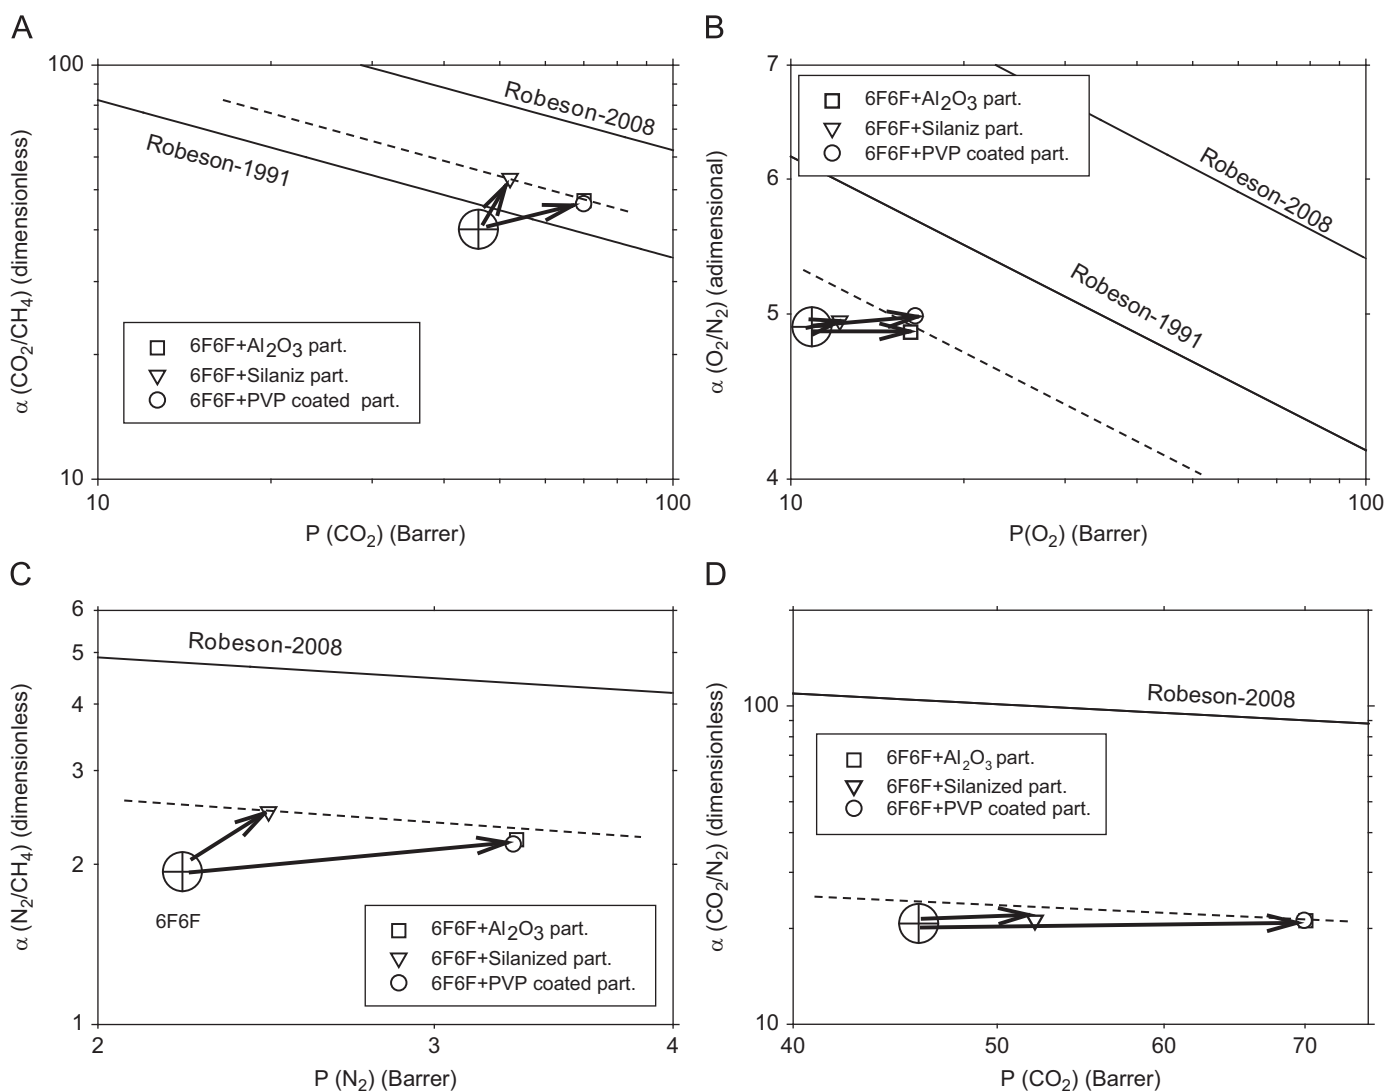


Fig. 7. Robeson's plots for the gas pairs: CO_2/CH_4 (A) O_2/N_2 (B) N_2/CH_4 (C) and CO_2/N_2 (D). The 1991 (when existing) and 2008 Robeson's bonds are shown. The big crossed circle corresponds to the polymeric matrix alone. Also a dashed line is drawn in parallel to these bond lines but passing close to the experimental points to help judging how the use of each particle improves the membrane results.

permeabilities are lower and the selectivity is higher across the sieve particles. This behavior has been studied and probed by Chung et al., 2007; Li et al., 2005 for particles of zeolite, which surface was treated similarly to some of these used here. They have also studied how the membrane morphology influence in the mixed matrix membrane performances, Widjojo et al., 2008.

In our case we have the same two kinds of modifications but our γ -alumina particles cannot be considered as sieves but rather as compact impenetrable phases. Moreover, in some cases we have coating layers that can modify strongly the properties of separation. Actually, what we think that is probably happening is

- i. When we add uncoated γ -alumina particles, the adherence with the 6FDA-6FpDA is poor (see Fig. 4) and the voids left are bigger than the sizes of the penetrant gases leading to an increase in permeability because the path of all the gases across the polymer is reduced.
- ii. When the PVP coated membranes are used, the PVP shell act as a high free volume interface and possibly disturbs the 6FDA-6FpDA matrix to increase its free volume. In this case the effect should be also a decrease in the effective length of selective membrane to be crossed.

- iii. Finally when we use silanized γ -alumina, the silane groups interacting with 6FDA-6FpDA should give a selective shell, according to the experimental results, when CH_4 is one of the permeant gases. Thus leading, in this case, to a Maxwell type mixture corresponding to the addition of a more permeable and selective medium to the polymeric matrix, Moore and Koros, 2005. Here, this highly permeable and selective material should be the halo formed by the silane and 6FDA-6FpDA chains. It is worth noting that when methane is not one of the penetrating gases, properties are totally different for the silanized particles that behave like those coated with PVP but corresponding to systems with smaller free volumes and leading to not so high increases in permeability but without significant changes in selectivity.

More information on the details of the processes appearing for different gases can be obtained from their diffusivities and solubilities through the mixed matrix membranes. These parameters can be obtained according to Eqs. (1) and (2). It is known that the diffusivity should decrease with the kinetic diameter of the gas and the solubility with its critical temperature, Recio et al., 2008; Sadeghi et al., 2009. The different behavior

of the gases used can be analyzed in terms of their kinetic diameter and critical temperature, which are shown in Table 3, Marchese et al., 2003; Breck, 1974. The so-obtained diffusivities and solubilities follow these general trends with the exception of CO₂ that has a much lower diffusivity should be expected according to its kinetic diameter as it is widely known, Sadeghi et al., 2009. These trends are shown in Fig. 8A and B.

In Fig. 9 the solubility selectivity is shown versus the diffusivity selectivity for all the membranes and gas pairs studied, defined as

$$\alpha_{ij} = \frac{P_i}{P_j} = \frac{D_i S_i}{D_j S_j} = \alpha_{ijD} \alpha_{ijS} \quad (3)$$

It can be seen that, for all the membranes, N₂/CH₄ is the gas pair with the most diffusive selectivity followed by CO₂/CH₄ and O₂/N₂ while CO₂/N₂ has a selectivity mostly determined by differences in solubility.

In order to study the effect in diffusivity and solubility selectivities of the different particles used it is better to analyze the corresponding increments of both these selectivities over those for the pure polymeric matrix, which are shown in Table 4. Assuming that, although the absolute errors in these determinations are high, the relative values of the magnitudes between the different membranes should be low, since they have been measured with the same device and under the same measurement conditions. Taking that into account, these values allow stating that

- When unmodified γ -alumina particles are added, the diffusivity increases strongly while the changes in solubility are much smaller.
- When PVP coated particles are used, the changes are similar to those obtained when the neat γ -alumina particles are used. In this case, diffusivities also increase strongly with a slight increase in solubilities.

Table 3
Kinetic diameters and critical temperature of the used gases.

Gas	CO ₂	O ₂	N ₂	CH ₄
Kinetic diameter, d_c (Å)	3.30	3.46	3.64	3.80
Critical temperature, T_c (K)	304.4	154.790	126.2	190.6

- Finally in the case of the silanized γ -alumina particles, the changes are much stronger for the solubility that increases for all the gases except methane. On the contrary, diffusivity slightly decreases for all the gases except for methane. This gas shows a relatively strong decrease of both diffusivity and solubility.

The exceptional behavior of methane can be partly attributed to its size. In effect, it is the biggest molecule among the studied gases as seen in Table 3. This could justify the decrease of diffusivity if the free volume of the silane shell consisted in smaller voids than those appearing in the polymeric matrix. The decrease in solubility, in spite of its relatively high critical temperature, could also be explained in terms of a reduction in

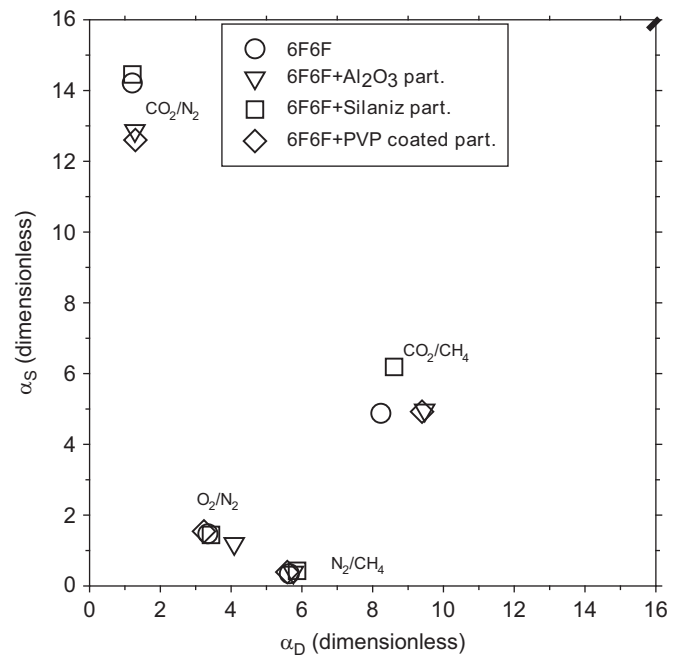


Fig. 9. Solubility selectivity versus the diffusivity selectivity for all the membranes and gas pairs studied. Note that over the diagonal the membrane selectivity is more determined by solubility than by diffusivity and the other way round below the diagonal.

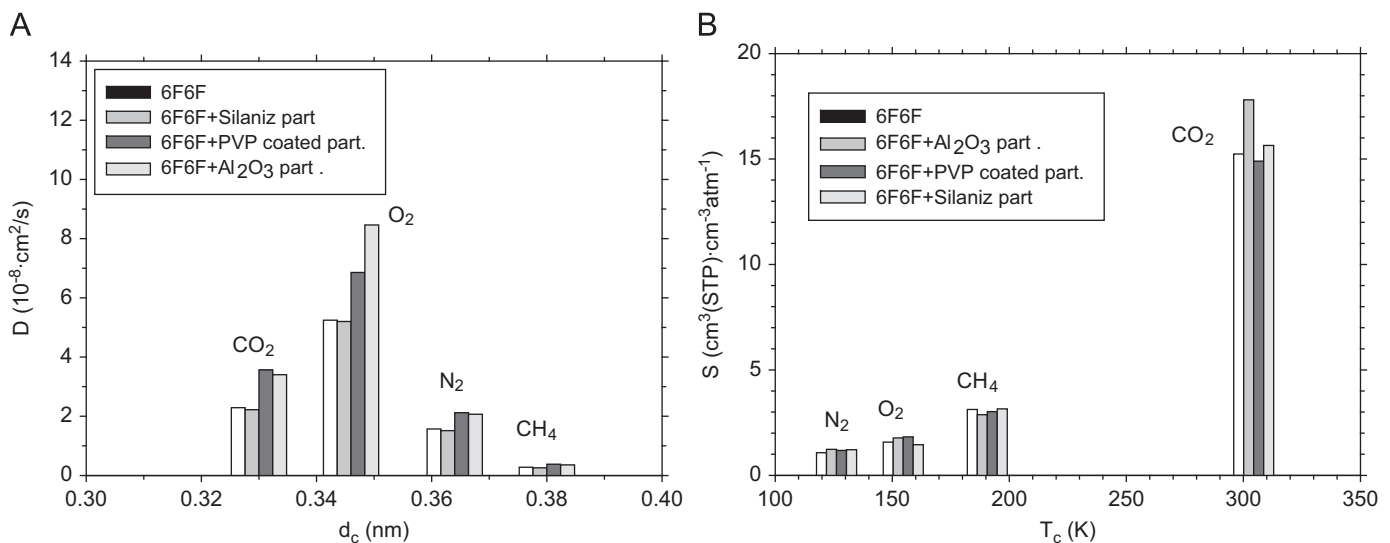


Fig. 8. Diffusivity versus the kinetic diameter for the gases and membranes used (A) and Solubility versus the critical temperature for the gases and membranes used (B).

Table 4

Change in diffusivity and selectivity of all the gases studied referred to that of the 6FDA-6FPDA when the different γ -alumina particles are included in the polymeric matrix.

γ -alumina particles	CO ₂	O ₂	N ₂	CH ₄
<i>Changes in diffusivity referred to that of the polymeric matrix (%)</i>				
Unmodified	48.7	61.3	31.9	29.3
Silanized	-2.8	-0.8	-3.4	-7.0
PVP coated	55.9	30.7	35.2	36.6
<i>Changes in solubility referred to that of the polymeric matrix (%)</i>				
Unmodified	2.7	-7.9	13.4	0.8
Silanized	16.9	12.8	14.9	-8.0
PVP coated	-2.2	15.7	10.2	-3.2

the size of the voids in such a way that CH₄ could not enter, and thus, it is not able to condense in a big proportion the overall free volume. By the way, this reduction in the size of the voids could also explain the increase in solubility for the other smaller gases because they could enter in the voids easily.

On the other hand, a low chemical compatibility with the silane chains could also explain the decrease of its solubility when silane shells coat the particles. Nevertheless, as shown in Fig. 3, the silanized particles, due to the way of their manufacture, have a lower amount of OH groups than those present in both the uncoated and the PVP coated particles. Then, these chains must have more polar character than the silanized ones. Thus, given that methane has the lower polarity among the studied gases, this should in fact lead to an increase in solubility for methane in the mixed matrix containing silanized particles rather than to a decrease as experimentally observed.

4. Conclusions

The inclusion of nanoparticles of γ -alumina (uncoated, silanized- or PVP-coated) in the 6FDA-6FPDA polymeric matrix allows an improvement of the permeability versus selectivity trade-off, for all the coatings and pairs of gases used because the resulting mixed-matrix membranes approach the upper bond in the Robeson's plot. Nevertheless, the extension and character of such improvement is different both qualitative and quantitatively for each kind of treatment of the particles and each pair of gases studied.

For all the pairs of gases there are quite similar improvements on gas separation properties but in different directions. In effect increases in permeability are observed when unmodified particles or PVP coated particles are used. While, in the case of mixed matrix membranes incorporating silanized particles is the selectivity which increases. Only for the O₂/N₂ pair, the increase in selectivity appearing for the silanized particles is not so effective in advancing towards the Robeson's upper bond when compared with the permeability enhancement registered for the unmodified and PVP coated particles.

It is worth noting that in the case of CO₂/CH₄ the old Robeson's line is crossed because the 6FDA-6FPDA polymeric matrix gas separation properties were good enough for this pair of gases.

Acknowledgements

Authors are grateful for the support of the Spanish National Plan of RD (projects MAT2005-04976, MAT2008-00619) and to the Junta de Castilla y León (Grupo de Excelencia GR18 and Va088/A08 Project). We are also grateful to the Project I142

Universidad Nacional del Comahue-Argentina and to the Spanish Agency of International Cooperation.

References

- Anson, M., Marchese, J., Garis, E., Ochoa, N., Pagliero, C., 2004. ABS copolymer-activated carbon mixed matrix membranes for CO₂-CH₄ separation. *J. Membr. Sci.* 243, 19–28.
- Barrer, R.M., Skirrow, G., 1984. Transport and equilibrium phenomena in gas-elastomer systems. I. Kinetic phenomena. *J. Polym. Sci.* 3, 549–563.
- Breck, D.W., 1974. Zeolite Molecular Sieves: Structure, Chemistry and Use. Wiley, New York, NY.
- Cecopieri-Gómez, M.L., Palacios-Alquisira, J., Domínguez, J.M., 2007. On the limits of gas separation in CO₂/CH₄, N₂/CH₄ and CO₂/N₂ binary mixtures using polyimide membranes. *J. Membr. Sci.* 293, 53–65.
- Chilingar, G.V., Robertson, J.O., Kumar, S., 1989. Surface Operations in Petroleum Production. Elsevier, Amsterdam, The Netherlands.
- Chung, T.S., Chan, S.S., Wang, R., Lu, Z., He, C., 2003. Characterization of permeability and sorption in Matrimid/C₆₀ mixed matrix membranes. *J. Membr. Sci.* 211, 91–99.
- Chung, T.S., Jiang, L.Y., Li, Y., Kulprathipanja, S., 2007. Mixed matrix membranes (MMMs) comprising organic polymers with dispersed inorganic fillers for gas separation. *Prog. Polym. Sci.* 32, 483–507.
- Coleman, M.R., Koros, W.J., 1999. Conditioning of fluorine-containing polyimides. 2. Effect of conditioning protocol at 8% volume dilation on gas-transport properties. *Macromolecules* 32, 3106–3113.
- Crank, J., 1975. The Mathematics of Diffusion, second ed Clarendon Press, Oxford.
- Daynes, H.A., 1920. The process of diffusion through a rubber membrane. *Proc. R. Soc. London* 97, 286–307.
- Favre, E., Morliere, N., Roizard, D., 2002. Experimental evidence and implications of an imperfect upstream pressure step for the time-lag technique. *J. Membr. Sci.* 207, 59–72.
- Fernández, L., Arranz, G., Palacio, L., Soria, C., Sánchez, M., Pérez, G., Lozano, A.E., Hernández, A., Prádanos, P., 2009. Functionalization of γ -alumina cores by polyvinylpyrrolidone: properties of the resulting biocompatible nanoparticles in aqueous suspension. *J. Nanopart. Res.* 11, 341–354.
- He, Z., Pinnau, I., Morisato, A., 2002. Nanostructured poly(4-methyl-2-pentyne)/silica hybrid membranes for gas separation. *Desalination* 146, 11–15.
- Jia, M.D., Peinemann, K.V., Behling, R.D., 1991. Molecular sieving effect of the zeolite-filled silicone rubber membranes in gas permeation. *J. Membr. Sci.* 57, 289–296.
- Khulbe, K.C., Matsuura, T., Lamarche, G., Kim, H.J., 1997. The morphology characterisation and performance of dense ppo membranes for gas separations. *J. Membr. Sci.* 135, 211–223.
- Li, Y., Chung, T.S., Cao, C., Kulprathipanja, S., 2005. The effects of polymer chain rigidification, Zeolite pore size and pore blockage on polyethersulfone (PES)-zeolite A mixed matrix membranes. *J. Membr. Sci.* 260, 45.
- Li, N.N., Fane, A.G., Ho, W.S.W., Matsuura, T., 2008. Advanced Membrane Technology and Applications. Wiley-Interscience, Hoboken, NJ, USA.
- Marchese, J., Anson, M., Ochoa, N.A., Prádanos, P., Palacio, L., Hernández, A., 2006. Morphology and structure of ABS membranes filled with two different activated carbons. *Chem. Eng. Sci.* 61, 5448–5454.
- Marchese, J., Garis, E., Anson, M., Ochoa, N.A., Pagliero, C., 2003. Gas sorption, permeation and separation of ABS copolymer membrane. *J. Membr. Sci.* 221, 185–197.
- Matteucci, S., Kusuma, V.A., Sanders, D., Swinnea, S., Freeman, B.D., 2008a. Gas transport in TiO₂ nanoparticle-filled poly (1-trimethylsilyl-1-propyne). *J. Membr. Sci.* 307, 196–217.
- Matteucci, S., Kusuma, V.A., Swinnea, S., Freeman, B.D., 2008b. Gas permeability, solubility and diffusivity in 1,2-polybutadiene containing brookite nanoparticles. *Polymer* 49, 757–773.
- Matteucci, S., Raharjo, R.D., Kusuma, V.A., Swinnea, S., Freeman, B.D., 2008c. Gas permeability, solubility, and diffusion coefficients in 1,2-polybutadiene containing magnesium oxide. *Macromolecules* 41, 2144–2156.
- Merkel, T.C., Freeman, B.D., Spontak, R.J., He, Z., Pinnau, I., Meadkin, P., Hill, A.J., 2002. Ultra-permeable, reverse-selective nanocomposite membranes. *Science* 296, 519–520.
- Merkel, T.C., He, Z., Pinnau, I., Freeman, B.D., Meakin, P., Hill, A.J., 2003. Effect of nanoparticles on gas sorption and transport in poly(1-trimethylsilyl-1-propyne). *Macromolecules* 36, 6844–6855.
- Moore, T.T., Koros, W.J., 2005. Non-ideal effects in organic-inorganic materials for gas separation membranes. *J. Mol. Struct.* 739, 87–98.
- Muñoz, D.M., de la Campa, J.G., de Abajo, J., Lozano, A.E., 2007. Experimental and theoretical study of an improved activated polycondensation method for aromatic polyimides. *Macromolecules* 40, 8225–8232.
- Nagel, C., Günther-Schade, K., Fritsch, D., Strunskus, T., Faupel, F., 2002. Free volume and transport properties in highly selective polymer membranes. *Macromolecules* 35, 2071–2077.
- Paul, D., DiBenedetto, A.T., 1965. Diffusion in amorphous polymers. *J. Polym. Sci. C* 10 (1), 17–44.
- Puri, P.S., 1996. Gas separation membranes current status. *La Chim. e l'Ind.* 78, 815–821.

- Recio, R., Lozano, A.E., Prádanos, P., Marcos, A., Tejerina, F., Hernandez, A., 2008. Effect of fractional free volume and t_g on gas separation through membranes made with different glassy polymers. *J. Appl. Polym. Sci.* 107, 1039–1046.
- Recio, R., Palacio, L., Prádanos, P., Hernández, A., Lozano, A.E., Marcos, A., de la Campa, J.G., de Abajo, J., 2006. Permeability and selectivity of 6FDA-6FpDA gas membranes prepared from different solvents. *Desalination* 200, 225–226.
- Recio, R., Palacio, L., Prádanos, P., Hernández, A., Lozano, A.E., Marcos, A., de la Campa, J.G., de Abajo, J., 2007. Gas separation of 6FDA-6FpDA membranes: effect of solvent on polymer surfaces and permselectivity. *J. Membr. Sci.* 293, 22–28.
- Robeson, L.M., 1991. Correlation of separation factor versus permeability for polymeric membranes. *J. Membr. Sci.* 62, 165–185.
- Robeson, L.M., 2008. The upper bound revisited. *J. Membr. Sci.* 320, 390–400.
- Rutherford, S.W., Do, D.D., 1997. Review of time-lag permeation technique as a method for characterization of porous media and membranes. *Adsorption* 3, 283–312.
- Sadeghi, M., Semsarzadeh, M.A., Moadel, H., 2009. Enhancement of the gas separation properties of polybenzimidazole (PBI) membrane by incorporation of silica nano particles. *J. Membr. Sci.* 331, 21–30.
- Sen, D., Kalıpcılar, H., Yılmaz, L., 2007. Development of polycarbonate based zeolite 4A filled mixed matrix gas separation membranes. *J. Membr. Sci.* 303, 194–203.
- Speight, J.G., 1999. *The Chemistry and Technology of Petroleum*. Marcel Dekker, New York, USA.
- Stookey, D.J., 2006. Gas separation membrane applications. In: Pereira-Nunes, S., Peinemann, K.V. (Eds.), *Membrane Technology in the Chemical Industry*. Wiley-VCH, Weinheim, Germany, pp. 119–150.
- Tartekin-Ersolmaz, S.B., Atalay-Oral, C., Tather, M., Erdem-Senatalar, A., Schoeman, B., Sterte, J., 2000. Effect of zeolite particle size on the performance of polymer-zeolite mixed matrix membranes. *J. Membr. Sci.* 175, 285–288.
- Van Krevelen, D.W., te Nijenhuis, K., 2009. *Properties of Polymers: Their Correlation with Chemical Structure; Their Numerical Estimation and Prediction from Additive Group Contributions*. Elsevier, Amsterdam, The Netherlands.
- Van Loo, S., Koppejan, J., 2008. *The Handbook of Biomass Combustion and Co-firing*. Earthscan, London, UK.
- Vu, D.Q., Koros, W.J., Miller, S.J., 2003a. Mixed matrix membranes using carbon molecular sieves I. Preparation and experimental results. *J. Membr. Sci.* 211, 311–334.
- Vu, D.Q., Koros, W.J., Miller, S.J., 2003b. Mixed matrix membranes using carbon molecular sieves II. Modelling permeation behaviour. *J. Membr. Sci.* 211, 335–348.
- Wang, X.Y., in't Veld, P.J., Lu, Y., Freeman, B.D., Sánchez, I.C., 2005. A molecular simulation study of cavity size distribution and diffusion in *para* and *meta* isomers. *Polymer* 46, 9155–9161.
- Widjojo, N., Chung, T.S., Kulprathipanja, S., 2008. The fabrication of hollow fiber membranes with double-layer mixed-matrix materials for gas separation. *J. Membr. Sci.* 325, 326–335.
- Yeom, C., Kim, B., Lee, J., 1999. Precise on-line measurements of permeation transients through dense polymeric membranes using a new permeation apparatus. *J. Membr. Sci.* 161, 55–66.
- Yoshida, W., Castro, R.P., Jou, J.D., Cohen, Y., 2001. Multilayer alkoxysilane silylation of oxide surfaces. *Langmuir* 17, 5882–5888.
- Zimmerman, C.M., Koros, W.J., 1997. Tailoring mixed matrix composite membranes for gas separations. *J. Membr. Sci.* 137, 145–154.